

Analysis of Machining Parameters on EDM of HCHCR-D2 Using Full Factorial Design

Vinit D Raut

Department of Mechanical Engineering, Mumbai University, Maharashtra-401305

Abstract— In this report the effect of Process parameters on material removal rate(MRR) and surface roughness of HCHCR-D2(high carbon high chromium steel) die steel are investigated as MRR and Surface roughness in W-EDM(wire electrical discharge machining) are of crucial importance and Full factorial Design and ANOVA techniques are used for optimization of parameters. For experimentation Pulse on time (Ton), Pulse off time (Toff), Peak current (Ip), and wire feed rate (Wf) are taken as input parameters while MRR and Surface roughness are taken as output parameters. For each experiment Surface roughness is calculated by using Surface finish tester and MRR is calculated by measuring the difference in weight of workpiece before and after machining with time required for machining.

Keywords: Wire electrical discharge machining, Material removal rate , Surface Roughness ,Full factorial Design ,HCHCR-D2 Material, ANOVA.

I. INTRODUCTION

1.1 Wire Electrical Discharge Machining Process:

Wire Electrical Discharge Machining (W-EDM) is widely used manufacturing process used to machine conductive materials due to its capability of producing intricate and complex shapes irrespective of hardness and toughness of material. It can produce more complex two and three dimensional shapes through conducting materials This process is extensively used in mould and die making industries, nuclear industry, aerospace industry etc.

In WEDM (wire electrical discharge machining) material removal takes place due to electro thermal process. A series of electrical pulses generated by pulse generator unit is applied between the work piece and travelling wire electrode which generate series of discrete sparks between the electrode and work piece. While the machining is continued, the machining zone is continuously flushed with water passing through the nozzles on both sides of the work piece.

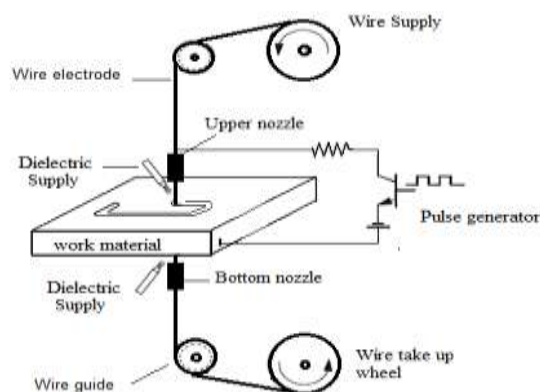


Fig 1: Schematic Representation of WEDM process

II. PROBLEM DEFINITION

In CNC Wire electrical discharge machine, Process parameters like pulse on time(Ton), pulse off time(Toff), Input Current(Ip), wire feed rate(Wf) play an important role as it affects the MRR (material removal rate) and Surface roughness. Most of the times this machines are operated by workers; If process parameters are not set properly then it results in low MRR as well as Surface finish. If at some point amount of stock removed from the electrode becomes greater than the amount being removed from the

work piece, the wire electrode breaks and discharge is stopped. The overall objective is to produce high quality product at low cost to the manufacturer. Optimization is a process that finds a best, or optimal, solution for a problem of process parameters is the best way to solve this problem. Taguchi L9 Orthogonal array and Grey Relational analysis used to set optimal set of parameters.

III. METHODOLOGY

3.1 Design of Experiment:

The design of experiments (or experimental design) is the design of any task that aims to describe or explain the variation of information under conditions that are hypothesized to reflect the variation. The term is generally associated with true experiments in which the design introduces conditions that directly affect the variation, but may also refer to the design of quasi-experiments, in which natural conditions that influence the variation are selected for observation.

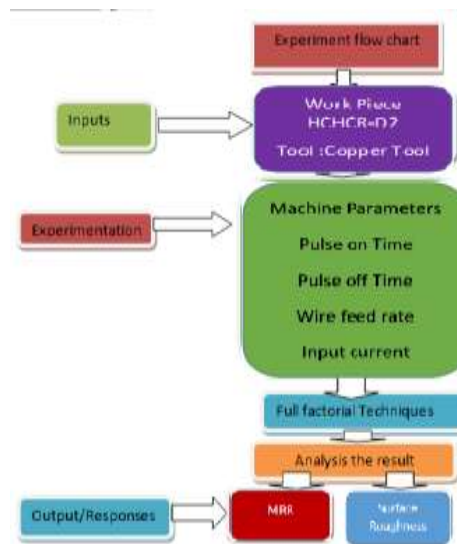


Fig 2 Methodology Flow Chart

3.2 Work piece Material:

The work piece material is HCHCR-D2 (high carbon high chromium steel) with dimension (Diameter 40mm, Thickness 26mm, weight 230gm) is used for experimentation. The Brass wire with diameter 0.25mm is used as electrode. Pure distilled water is used as dielectric medium. Fig. 4.2 shows actual working zone of WEDM and Table 3.2 shows the Percentage of Composition of HCHCR-D2.

Table 1
Shows the Percentage of Composition of HCHCR-D2.

| C | Mn | Cr | Si |
|---|----------|----|----------|
| 2 | 0.2-0.35 | 12 | 0.2-0.35 |

3.3 ELECTRA Wire Cut Electric Discharge Machine:

ELECTRA Wire Cut Electric Discharge Machine (Manufactured by Electronica Machines Tools Ltd) is used in this investigation. Once wire is wound on the wire drum, that particular amount of wire is used for all experiments of each material and it has been replaced once the material is changed. Work material is tightly clamped on working table with the help of suitable fixture so as to avoid any relative motion between the work piece and electrode. Constant dielectric flow is ensured during the experimentation. Fig.3 shows the CNC WEDM machine used for experimentation.

3.4 ELECTRA Wire Cut Electric Discharge Machine:

ELECTRA Wire Cut Electric Discharge Machine (Manufactured by Electronica Machines Tools Ltd) is used in this investigation. Once wire is wound on the wire drum, that particular amount of wire is used for all experiments of each material and it has been replaced once the material is changed. Work material is tightly clamped on working table with the help of suitable fixture so as to avoid any relative motion between the work piece and electrode. Constant dielectric flow is ensured during the experimentation. Fig.3 shows the CNC WEDM machine used for experimentation.



Fig. 3 Work piece



Fig.4: Working zone of Wire electrical discharge machining

IV. CASE STUDY

In experimental study 8mm hole is created in the work piece with brass wire. MRR (material removal rate) is calculated by measuring the difference in weight of work piece before and after machining and time required to create a through hole. Surface roughness (Ra) is calculated by MITUTOYO Surface Tester Master.

4.1 Taguchi L9 Orthogonal Array:

Table 2 shows process parameters with their level for this experiment. The Taguchi method involves reducing the variation in a process through robust design of experiments. The overall objective of the method is to produce high quality product at low cost to the manufacturer.

Table 2
 Process parameters with their levels.

| Sr. No | Process Parameters | Unit | Level 1 | Level 2 | Level 3 |
|--------|----------------------|-------|---------|---------|---------|
| 1 | Pulse on time(Ton) | µs | 127 | 128 | 129 |
| 2 | Pulse off time(Toff) | µs | 45 | 46 | 47 |
| 3 | Input current(Ip) | A | 210 | 220 | 230 |
| 4 | Wire feed(Wf) | m/min | 3 | 4 | 5 |

Taguchi Proposed to acquire the characteristics data by using orthogonal arrays, and to analyse the performance measure from data to decide the optimal process parameters. The designed matrix of input parameters with output parameters such as MRR (material removal rate) and Surface roughness (Ra) for HCHCR-D2 (High carbon high chromium steel). Selection of a particular OA is based on the number of levels of various factors. Here, Number of levels (L)=3 and No of factors(f)=4 therefore Degree of Freedom (DOF) can be calculated by using Eq. as $DOF = f \times (L-1) = 8$, the orthogonal array should be equal to or greater than DOF, here $9 > 8$ hence L9. Each machining parameter is assigned to a column of OA and 9 machining parameter combinations are designed.

Table 3
L9 orthogonal Arrey

| Trial No | Ton | Toff | Ip | Wf | MRR (gm/min) | Ra(μm) |
|----------|-----|------|-----|----|--------------|--------|
| 1 | 127 | 45 | 210 | 3 | 0.66 | 1.9 |
| 2 | 127 | 46 | 220 | 4 | 0.92 | 2.1 |
| 3 | 127 | 47 | 230 | 5 | 1 | 2.7 |
| 4 | 128 | 45 | 220 | 5 | 0.66 | 1.8 |
| 5 | 128 | 46 | 230 | 3 | 1.06 | 1.9 |
| 6 | 128 | 47 | 210 | 4 | 0.82 | 1.3 |
| 7 | 129 | 45 | 230 | 4 | 1.12 | 1.4 |
| 8 | 129 | 46 | 210 | 5 | 0.82 | 1.8 |
| 9 | 129 | 47 | 220 | 3 | 1.12 | 1.5 |

4.2 Design of experiment using Full factorial

Full factorial experiment is an experiment whose design consists of two or more factors, each with discrete possible values or "levels", and whose experimental unit take on all possible combinations of these levels across all such factors. A full factorial design also called as a fully crossed design. Such an experiment allows the examiner to study the effect of each factor on the response variable, as well as the effects of interactions between factors on the response variable. In the experiment using four factors and each are three levels then total number of trials to be showed is 9.

In this study, an L9 based on full factorial are used machining parameters like pulse current, pulse on time, duty cycle and voltage setting were diverse to conduct 9 different trials and the measurements weights of the work piece were taken for calculation of MRR. Minitab software was used to analysis the findings. In this experiment Minitab software design are selected is 3 level design and number of factors is four. The flow chart of the experiment is shown in Fig.1. Experimental observation data are described.

V. RESULTS AND DISCUSSIONS

5.1 Influence of MRR

The Main effect plot for of MRR is shown in Fig. 5. The Pulse on time (Ton) and Input Current(Ip) is inversely proportional to MRR in the range of 1 to 5A. This is expected because an increase in pulse current produces strong spark, which produces the higher temperature, causing more material to melt and erode from the work piece. The duty cycle and voltage have no significant effect on MRR. The residual plot of MRR is shown in Fig. 3, where each plot exhibits the error between four different machining parameters like Ip, Ton and Tau and V. This implies that the effect of one factor is dependent upon another factor. It is also confirmed by the ANOVA table (Table 3).

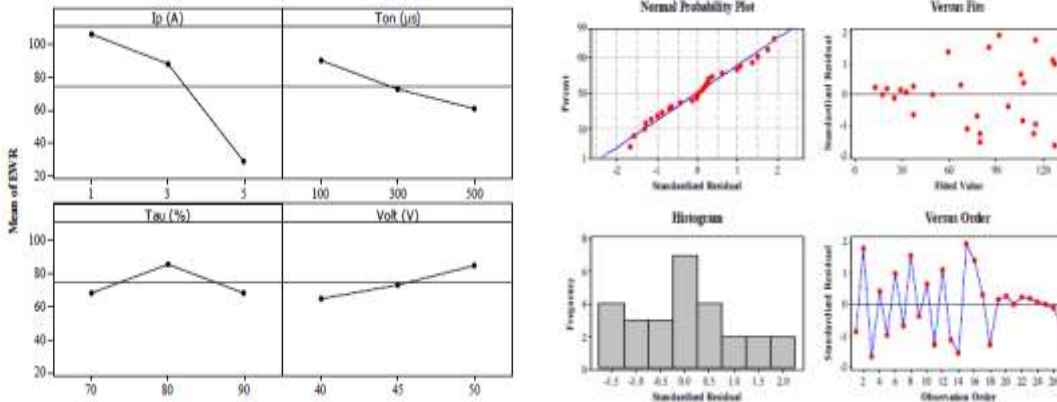


Fig 5 Influence of MRR

5.2 Influence of SR

In the process of machining minimum over cut is required for better result. The effect of various machining parameters such as discharge current, pulse on time, wire feed rate and Pulse on time(Ton) on over cut is presented in the main effect plot shown in Fig.3. and error are plotted are Fig 6. In the analysis of overcut discharge current, pulse on time and Pulse on time Ton has significantly affected. Voltage is not affected significantly that is confirm by ANOVA table of surface roughness

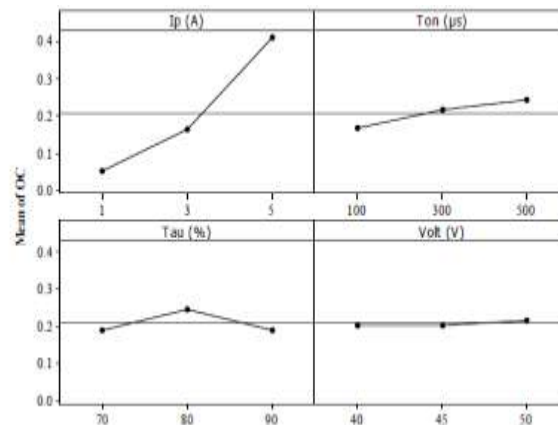


Fig 6 Influence of SR

VI. CONCLUSION

In the present work of study the effect of machining responses are Material Removal Rate and Surface Roughness of the HCHCR-D2 tool steel component using full factorial design with internal flushing system have been investigated for EDM process.

1. Pulse current is most influencing factor for MRR and then pulse duration and the voltage and duty cycle has no significant affected.
2. In the case of the dimensional accuracy, the measurement of Surface Roughness discharge current and pulse duration is given the significant effect. Then the input current (Ip) has slightly effect the dimensional accuracy, but wire feed rate(Wf) has no significant affected Acknowledgements

REFERENCES

[1] Prasenjit Datta and Bikash Choudhary, "Optimization of Wire edm machining in Inconal 800 using Grey relational analysis", Proceeding of IRF international conference, pp.17-21,2015.

- [2] G.Antony Casmir and S. Ashok kumar, "Optimization of wire cut edm using hchcr by taguchi analysis", International conference on recent advancement in mechanical engineering & technology, pp.54-57, 2015.
- [3] Timur Rizovich Ablyaz and Vladimir Aleksandrovich Ivanov, "Research of Electrical Discharge Machining Process of Wear Resistance Coatings Obtained By Beam Deposit Process", journal of Modern Applied Science, vol 9, pp.257-265, 2015.
- [4] Amit Chauhan and Onkar Singh Bhatia, "Optimization of multiple machining characteristic in wedm of nickel based super alloy using of taguchi method and grey relational analysis", International Journal of Advanced Technology in Engineering and Science, vol.3, pp.187-193, 2015.
- [5] Vijay D Patel and Dr. D M Patel, "A Study and Investigation on SR in Wire Electrical Discharge Machining using Molybdenum Wire", International Journal On Innovative Research in Science, Engineering and Technology, vol 3, pp.45-56, 2014.
- [6] Brajesh Lodhi and Sanjay Agarwal, "Modeling of Wire Electrical Discharge Machining of AISI D3 Steel using response Surface Methodology", 5th International manufacturing technology, Design and Research Conference (AIMTDR 2014) December 12th-14th, IIT 2014.